

CHEMICAL RESISTANCE OF TYPICAL HPLC (HIGH-PRESSURE LIQUID CHROMATOGRAPHY) SOLUTIONS

**Bal Seal Engineering UP-40 Polyethylene and
GFPA-PTFE Materials**

Technical Report
TR-60B (Rev. 5; 05-10-02)
(100-27-8)



19650 Pauling
Foothill Ranch, CA 92610-2610
Tel (949) 460.2100
Fax (949) 460.2300
Email: sales@balseal.com
www.balseal.com

Bal Seal Engineering Europe B.V.
Jollemanhof 16, 5th Floor
1019 GW Amsterdam
The Netherlands
Tel +31 20 638 6523
Fax +31 20 625 6018
Email: ordersbv@balseal.nl

TABLE OF CONTENTS

- 1.0 Summary
- 2.0 Test procedures
- 3.0 Results
 - 3.1 Chemical resistance of BAL™ Seal UP-40 polyethylene material
 - 3.2 Chemical resistance of BAL™ Seal GFPA-PTFE material

The information, descriptions, recommendations and opinions set forth herein are offered solely for your consideration, inquiry, and verification and are not, in part or in whole, to be construed as constituting a warranty, expressed or implied, nor shall they form or be a part of the basis of any bargain with Bal Seal Engineering. If any sample or model was shown to or provided by Buyer/User, such sample or model was used merely to illustrate the general description and type of goods. Such use is not to be construed as a warranty that the goods will conform to the sample or model. Furthermore, THE IMPLIED WARRANTY OF MERCHANTABILITY AND FITNESS FOR A PARTICULAR PURPOSE AND ALL OTHER WARRANTIES, IMPLIED OR EXPRESSED, ARE EXCLUDED AND SHALL NOT APPLY. This document provides product options for further investigation by Buyers/Users having technical expertise. The Buyer/User, through its own analysis and testing, is solely responsible for making the final selection of the products and for assuming that all performance, safety and warning requirements for the application are met. It is recommended that Buyers/Users run evaluation testing under actual service conditions to determine whether proposed Bal Seal products are suitable for the intended purpose. Nothing contained herein or in any of our literature shall be considered a license or recommendation for any use that may infringe patent rights. (LE-17)

PATENTS: The items described in this report include products that are the subject of the following issued United States patents: 5,979,904; 5,994,856; 6,050,572; 5,984,316; 6,161,838 and others, as well as foreign patents or products where patents are pending. (LE-88G)

©Copyright 2002, Bal Seal Engineering Co., Inc. U.S.A.

Use or disclosure of data contained on this sheet is subject to the restrictions contained in the disclaimer located in the Table of Contents of this report.

1.0 SUMMARY


Tests have been conducted at Bal Seal Engineering Company, Inc., to determine the chemical resistance of BAL Seal UP-40 polyethylene and GFPA-PTFE materials. These materials are widely used as the piston seal in HPLC (high-pressure liquid chromatography) pumps.

The data has been condensed to indicate the changes in material properties after material samples were immersed in various chemicals for 168 hours. Changes in dimension, weight, tensile strength, and elongation are reported.

In general, distinct changes in material properties tend to affect the performance of seals made from the same material. For example, significant dimensional changes occurring when a material is immersed in a chemical are likely to affect the frictional properties of the seal. Significant tensile and elongation property changes are likely to affect the seal wear properties.

2.0 TEST PROCEDURES

The tests were conducted per Bal Seal Engineering specification MT-12. A test specimen was immersed in various chemicals at ambient temperature for 168 hours (Figure 1).

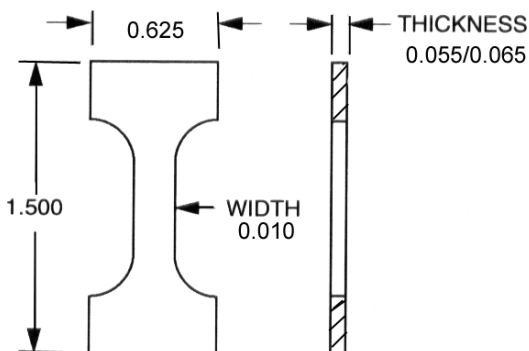

Typical Test Specimen

Figure 1

Three seal material samples were tested in each chemical. These samples were measured, weighed and soaked in the chemicals for 168 hours. The samples were then removed from the media. Immediately thereafter, each sample was tested to determine the tensile and elongation properties. The tested samples were dried and the weight and weight variation recorded. (Request Bal Seal Engineering Research Report #58-45-1)

3.0 RESULTS

The results of the three samples were averaged to obtain the final values. The tensile strength and elongation values were compared with the three control samples taken from the same bar of material. The data presented in the following tables is based on retention of tensile and elongation properties retention and dimension and weight changes after exposing the material to the chemical at ambient temperature for 168 hours. The charts display the chemical resistance of BAL Seal materials UP-40 polyethylene and GFPA-PTFE to various representative media. In actual use, other factors, such as pressure, temperature and velocity, also affect the performance of BAL Seals.

3.1 Chemical resistance of BAL™ Seal UP-40 polyethylene material

BAL Seal UP-40, an FDA compatible* polyethylene composition, provides very good wear resistance in aqueous solutions; however, it has specific chemical resistance limitations. The results of the UP-40 material testing are shown below in Table 1.

* For a description, request Bal Seal Engineering Research Report #607-50-17.

Use or disclosure of data contained on this sheet is subject to the restrictions contained in the disclaimer located in the Table of Contents of this report.

Chemical Resistance of UP-40 Polyethylene				
Chemical	Weight Change (%)	Dimension Changes (Average of width and thickness %)	Tensile Strength Retention (%)	Elongation Retention (%)
Alcohols	+ 0.06	+ 1.2	89	94
Ethylene glycol	+ 0.19	0.0	92	97
Isopropyl alcohol	+ 0.06	- 0.8	93	84
Methyl alcohol				
Aqueous Solutions	+ 0.07	+ 2.6	95	104
Distilled water				
Aromatics	+ 5.78	+ 2.5	113	70
Benzene	+ 7.01	+ 2.5	88	96
Toluene				
Chlorinated Solvents	+ 15.23	+ 3.4	82	89
Carbon tetrachloride	+ 6.03	+ 1.7	101	89
Dichloromethane	+ 3.91	+ 1.2	92	101
Freon TF	+ 11.77	+ 2.4	103	89
Trichloroethylene				
Ethers	+ 5.93	+ 3.3	86	87
Tetrahydrofuran				
Hydrocarbons	+ 5.21	+ 0.8	104	100
Hexane	+ 0.23	- 2.3	79	101
Mineral oil				
Nitriles	+ 0.09	+ 1.6	97	96
Acetonitrile				
Miscellaneous	0.00	+ 0.8	110	92
Alconox detergent	- 0.06	+ 2.5	95	104
Triethylene glycol				

Table 1
Property changes of BAL™ Seal UP-40 material when immersed in various chemicals for 168 hours per Bal Seal Engineering Specification MT-12

Use or disclosure of data contained on this sheet is subject to the restrictions contained in the disclaimer located in the Table of Contents of this report.

3.2 Chemical resistance of BAL™ SEAL GFPA-PTFE material

BAL Seal GFPA-PTFE, a graphite fiber-filled PTFE-based material, has excellent wear resistance in high-pressure, high-temperature and high-speed applications. This material is particularly suited for applications where high chemical resistance and good wear resistance are needed. BAL Seal GFPA-PTFE material requires that the piston be made from sapphire, TZP or other ceramic-type materials. Results of GFPA-PTFE material testing are shown below in Table 2.

Chemical Resistance of GFPA-PTFE				
Chemical	Weight Change (%)	Dimension Changes (Average of width and thickness %)	Tensile Strength Retention (%)	Elongation Retention (%)
Alcohols				
Ethylene glycol	+ 0.03	0.0	87	128
Isopropyl alcohol	+ 0.28	0.0	87	92
Methyl alcohol (58-45-1)	+ 0.29	+ 0.8	96	84
Aqueous Solutions				
Distilled water	+ 0.03	0.0	113	98
Aromatics				
Benzene	+ 0.60	+ 1.3	98	114
Toluene	+ 0.85	+ 0.8	93	82
Chlorinated Solvents				
Carbon tetrachloride	+ 1.33	0.0	99	118
Dichloromethane	+ 2.17	+ 1.6	110	89
Freon TF	+ 4.03	+ 2.4	82	177
Trichloroethylene	+ 2.87	+ 0.7	116	78
Ethers				
Tetrahydrofuran	+ 1.05	+ 0.0	89	85
Hydrocarbons				
Hexane	+ 0.68	+ 0.9	122	94
Mineral oil	+ 0.48	0.0	80	155
Nitriles				
Acetonitrile (58-45-1)	+ 0.35	- 0.8	96	87
Miscellaneous				
Alconox detergent	+ 0.07	0.0	95	78
Triethylene glycol	- 0.01	0.0	85	92

Table 2: Property changes of BAL™ Seal GFPA-PTFE material when immersed in various chemicals for 168 hours per Bal Seal Engineering Specification MT-12.

Use or disclosure of data contained on this sheet is subject to the restrictions contained in the disclaimer located in the Table of Contents of this report.